



UNIVERSITÀ DEGLI STUDI DI TRENTO

DEPARTMENT OF INDUSTRIAL ENGINEERING

Via Sommarive 9, 38123 Trento, ITALY

Test report: Uptec Profilitec

Trento, February 25th 2019

Applicant: Profilitec S.p.A.
Application: Specimen received at 28/01/2019
Material: Modular pedestals (SUPAS4-58/88) made of PP / 15% calcium carbonate.
Required test: Uniaxial compression test at constant speed and measurement of the compression load of the specimen and the displacement of the testing machine's crossbar at the break of the specimen. Moreover, the stiffness of the specimen was measured in the linear part of the load-displacement curve.
Testing method: Compression test was performed on 3 specimens for each sample. The components of the pedestal had been assembled, the height of the specimen was regulated according to Table 1 and the 4 tabs on top of the pedestal were removed before the test.
Specimens were placed on a flat aluminum plate provided by Profilitec S.p.A. Two screws had been used for the alignment of the pedestal inside the machine avoiding any possible misalignments. The upper plate was a circular and flat one provided by Instron.
An electro-mechanical testing machine, Instron 5969, was used to perform uniaxial compression tests under displacement control. Load was applied with a constant displacement rate of $1.67 \cdot 10^{-3}$ m/s. Test was stopped when a sharp load drop was measured that indicated the breakage of the pedestal. A load cell with a load capacity of 50 kN was employed to measure and record the force during the test.
Stiffness of the specimens was calculated in the linear part of the load-displacement curve, in particular, it was taken in account the part of the curve between 2.5 kN and 5 kN.
Test activities were carried out on February 20th, 2019. Tests were done inside a thermostatic chamber Instron at -20°C. Specimens were conditioned at -20°C for 12 hours before being tested.

The executor of the test
ing. Daniele Rigotti

The responsible for the laboratory
prof. Alessandro Pegoretti



Table 1. Sample identification.

Test	Model	N° tests	H (mm - inches)	Head	Plate	T (°C)	Speed (mm/min)
B3	SUPAS4-58/88	3	88 – 3-15/32	Fixed	Horizontal	-20	100

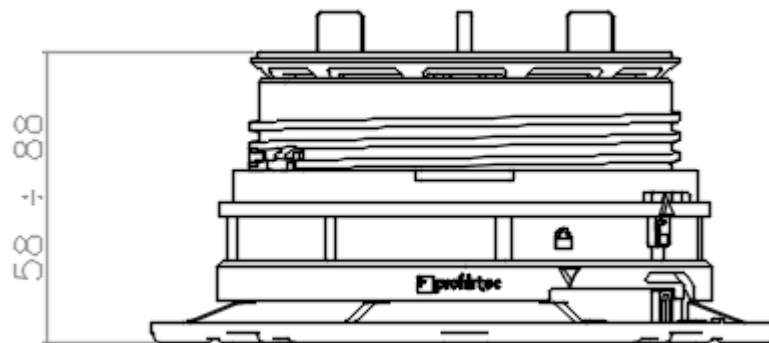


Figure 1. Specimen configuration.



Test results:

Table 2. Test result for sample B3.

Specimen	Stiffness (2.5-5kN) (kN/mm)	Load at break (kN)	Load at break (lbF)	Displacement at break (mm)
B3_1	7.71 ± 0.06	20.77	4669.28	3.48
B3_2	8.12 ± 0.07	22.16	4981.77	3.50
B3_3	8.24 ± 0.08	22.64	5089.67	3.60
Mean	8.02 ± 0.27	21.86 ± 0.97	4914.32 ± 218.06	3.53 ± 0.06

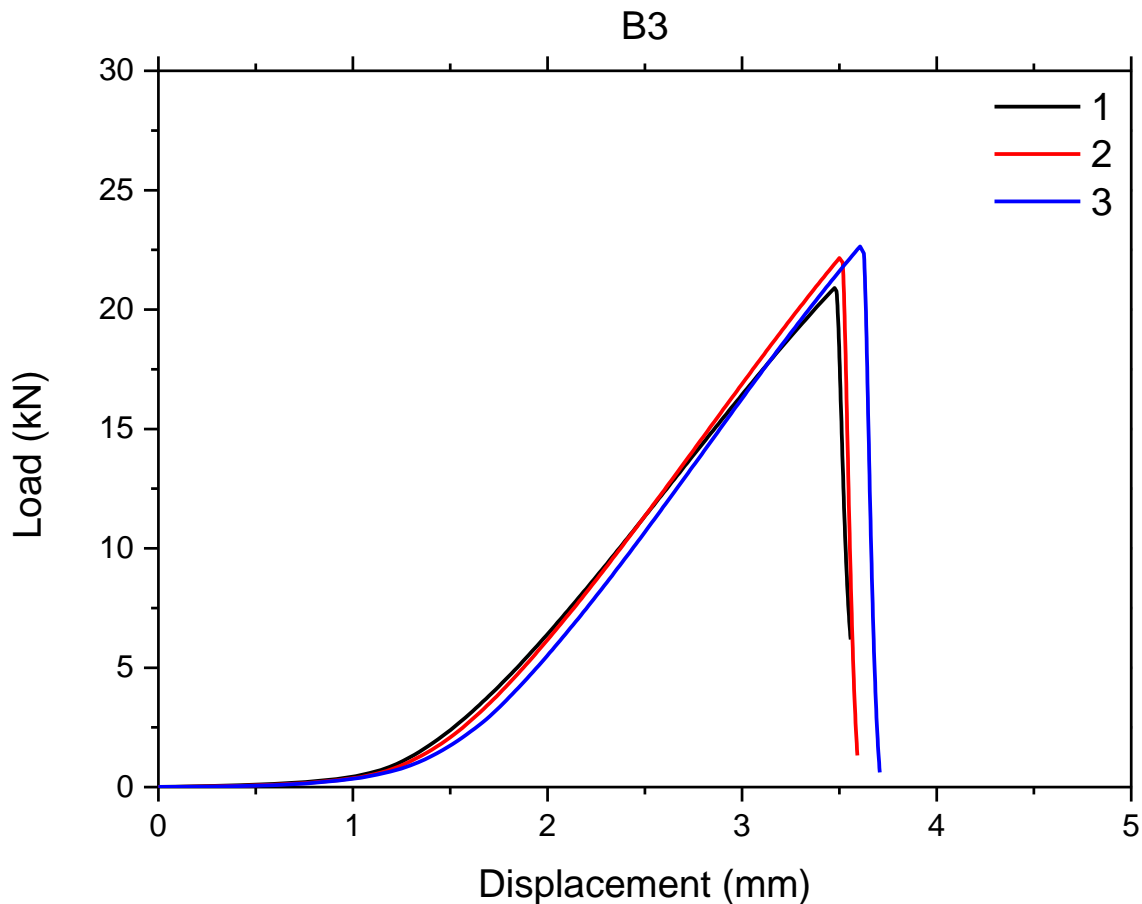


Figure 2. Load - displacement curves for sample B3.